

ACCEPTED MANUSCRIPT

Synthesis of ZnO Nanoarrays on Carbon Fibers using Combined Atomic Layer Deposition and Hydrothermal Methods

To cite this article before publication: Jingyu Wang *et al* 2018 *Mater. Res. Express* in press <https://doi.org/10.1088/2053-1591/aac845>

Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2018 IOP Publishing Ltd.

During the embargo period (the 12 month period from the publication of the Version of Record of this article), the Accepted Manuscript is fully protected by copyright and cannot be reused or reposted elsewhere.

As the Version of Record of this article is going to be / has been published on a subscription basis, this Accepted Manuscript is available for reuse under a CC BY-NC-ND 3.0 licence after the 12 month embargo period.

After the embargo period, everyone is permitted to use copy and redistribute this article for non-commercial purposes only, provided that they adhere to all the terms of the licence <https://creativecommons.org/licenses/by-nc-nd/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions will likely be required. All third party content is fully copyright protected, unless specifically stated otherwise in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

Synthesis of ZnO Nanoarrays on Carbon Fibers using Combined Atomic Layer Deposition and Hydrothermal Methods

Jingyu Wang¹, Binbin Weng^{2*}, Preston Larson³, Yingtao Liu^{1*}

¹School of Aerospace & Mechanical Engineering, University of Oklahoma, Norman 73019, USA

²School of Electrical and Computer Engineering, University of Oklahoma, Norman 73019, USA

³Samuel Roberts Noble Microscopy Laboratory, University of Oklahoma, Norman 73019, USA

*Corresponding author emails: Yingtao Liu, yingtao@ou.edu; Binbin Weng, binbinweng@ou.edu

Abstract

The paper presents the synthesis and characterization of zinc oxide (ZnO) nanoarrays on carbon fiber fabrics using the combined atomic layer deposition (ALD) and hydrothermal methods. A conformal ZnO seed layer was first synthesized using the ALD method on carbon fiber surfaces, then characterized by field emission scanning electron microscope (FESEM). ZnO nanoarrays were grown on the carbon fibers using the hydrothermal method. The morphology of ZnO nanoarrays in the form of nanowires and nanorods was controlled by adjusting hydrothermal synthesis parameters, including the concentration of chemical reagents and solution temperature. The FESEM characterization showed that the synthesized ZnO nanowires and nanorods had a wurtzite structure and uniformity distributed on the surface of carbon fibers. The length to diameter ratios of the ZnO nanoarrays were controlled between 44 and 270. The thermogravimetric analysis tests showed that the growth of ZnO nanoarrays added about 10% additional weight to the carbon fibers.

Keywords: zinc oxide nanoarray; carbon fiber; atomic layer deposition; hydrothermal method

1. Introduction

Recently light-weight structural composite materials have attracted significant attention due to their high strength-to-weight ratio, corrosion resistance, and design flexibility [1]. Integrating nanomaterials and nanostructures within conventional fiber reinforced composites provides a promising approach to improve composite properties. Carbon felt and carbon nanotubes have been synthesized on continuous structural fiber fabrics [2, 3]. Vertically aligned zinc oxide (ZnO) nanowires have been synthesized on natural fibers, such as cotton fibers [4-6] and jute fibers [7], and synthetic fibers, such as poly(acrylonitrile) fibers [8] and polyester fibers [9]. In particular, structural fibers, including carbon fibers [10-12] and aramid fibers [13-15] with vertically aligned nanowires, can result in advanced composite materials with enhanced mechanical properties due to the increased interfacial area between fiber and polymer matrix. Additionally, the piezoelectric properties of ZnO nanowires can also lead to load sensing functions for *in-situ* structural health monitoring and prognostics in complex composite structures [16-19].

Most current approaches to growing ZnO nanoarrays on carbon fiber fabrics are based on the dip-coating method that can only attach ZnO seeds to substrates by weak van der Waals forces in a wet chemical environment [2-9]. In addition, considering the strong hydrophobic properties and the cylindrical shape of the carbon fibers, it is challenging to deposit ZnO seeds in a good uniformity, conformity, and controlled crystal orientation using the dip-coating method.

In recent years, an emerging technique called atomic layer deposition (ALD) has become popular because it offers advantages, such as high degree of conformity, atomic-scale thickness controllability,

perfect stoichiometric uniformity, low impurity contamination, and low growth temperature [20-22]. Therefore, in order to avoid the issues associated with the dip-coating method, in this paper the ALD method was adopted to produce uniform and high-quality ZnO seed layers on carbon fiber fabrics. Then, we focused on studying the hydrothermally synthesized, vertically aligned ZnO nanoarrays on carbon fiber fabrics. Various hydrothermal growth parameters were investigated, including reaction temperature and concentration of chemical reagents, and the properties of ZnO nanoarrays coated carbon fiber fabrics were characterized using field emission scanning electron microscope (FESEM), thermogravimetric analysis (TGA) and energy-dispersive X-ray spectroscopy (EDX). We believe that the developed carbon fiber fabrics with ZnO nanoarray coatings will lead to the development of advanced composite materials with enhanced mechanical properties and potential load sensing capabilities.

2. Experiments

2.1. Materials

Unless otherwise stated, all the following listed materials and reagents were used as received. Plain weave carbon fiber fabrics were purchased from Fibre Glax. Diethylzinc and deionized water were purchased from Sigma–Aldrich and used for the ZnO seeding via ALD. Trichloroethylene (TCE, 99%), zinc nitrate hexahydrate ($\text{Zn}(\text{NO}_3)_2$, 99%) and hexamethylenetetramine (HMT, 99%) were purchased from Sigma–Aldrich and used in the hydrothermal synthesis of ZnO nanoarrays on carbon fiber fabrics.

2.2. Synthesis of ZnO nanoarrays on carbon fiber fabrics

A two-step synthesis approach was developed to grow vertically aligned ZnO nanowires on carbon fiber fabrics. First, the ALD method was used to deposit the ZnO seed layer on carbon fiber fabrics. Then, a low temperature hydrothermal method was employed as the second step to synthesize ZnO nanoarrays in the forms of nanowires and nanorods. To obtain an optimal ALD procedure, the seed layer was first grown on a silicon substrate, and characterized using atomic force microscope (AFM), X-ray diffraction (XRD), and FESEM. The detailed synthesis procedure has been reported in our previous publication [23]. The identified nucleation procedure was employed to deposit the ZnO seeds on carbon fiber fabrics, followed by FESEM characterization of the seed morphology.

In the second step, carbon fiber fabrics were degreased by dipping them into TCE and methanol solvents, respectively, for 10 minutes under ultrasonic agitation, then washed under running deionized water for 10 minutes, and finally dried in an environmental oven. $\text{Zn}(\text{NO}_3)_2$ and HMT aqueous solutions were prepared. Each was stirred at 600 rpm for 10 minutes at 55 °C, then mixed together and stirred at 600 rpm for 10 minutes at 55 °C. The solution was stored in a water bath at 90 °C for 1 hour to consume impurities. Finally, the carbon fiber fabrics were submerged into the prepared solution to hydrothermally synthesize ZnO nanoarrays. Detailed solution concentrations and hydrothermal growth temperature are listed in Table 1. The morphology of ZnO nanoarrays was studied using FESEM to characterize the average diameters and length to diameter ratio of ZnO nanoarrays. The elemental composition of the carbon fibers before and after ZnO nanoarrays coating were studied by EDX, the ZnO crystal orientation on the synthesized ZnO nanoarrays were tested by XRD, and the decomposition property and weight ratio of the ZnO on carbon fibers were then characterized using TGA.

Table 1. Experimental procedures used in hydrothermal syntheses of ZnO nanoforest on carbon fiber fabrics

Sample Name	$\text{Zn}(\text{NO}_3)_2$ Concentration (mMol/L)	HMT Concentration (mMol/L)	Growth Temperature (°C)
A1	25	25	70
A2	50	50	70

A3	100	100	70
B1	25	25	80
B2	50	50	80
B3	100	100	80

3. Results and Discussions

The identification of the optimal ALD procedure to deposit a thin layer of ZnO seeds on the substrate is a critical aspect of this paper. ZnO seeds were uniformly deposited on the silicon substrate, as shown in the FESEM (Fig. 1 a) and AFM (Fig. 1 b.) images. The same experimental procedure was adopted to deposit ZnO seed layer on carbon fiber fabrics. The FESEM image of the uniformly deposited ZnO seeds on a single carbon fiber was shown in Fig. 1 c. XRD tests were used to validate the crystal structures of the ZnO seeds and synthesized ZnO nanowires. Both the ZnO seeds grown on Si wafer (Fig. 1 d) and carbon fibers (Fig. 1 e) were tested first. When ZnO seeds were deposited on a flat Si wafer, the ZnO diffraction peaks in the XRD pattern proved the poly-crystalline nature of the thin film. Meanwhile, contrasting with the two weak (100) and (110) peaks, the dominant (002) diffraction peak indicated that the thin film was primarily grown in the c-axis orientation. Such optimized material quality will ensure high quality ZnO nanoarray growth in the hydrothermal growth process. When ZnO seeds were coated on carbon fiber, more diffraction peaks were detected in XRD. The (002) diffraction peak was still clear, however, the (100) and (101) diffraction peaks were also observed mainly due to the curved carbon fiber surface. The same XRD pattern was observed in ZnO nanowires compared to ZnO seeds on carbon fiber fabrics. During the hydrothermal treatment, all the ZnO diffraction peaks were enhanced, as shown in Fig. 1 f.


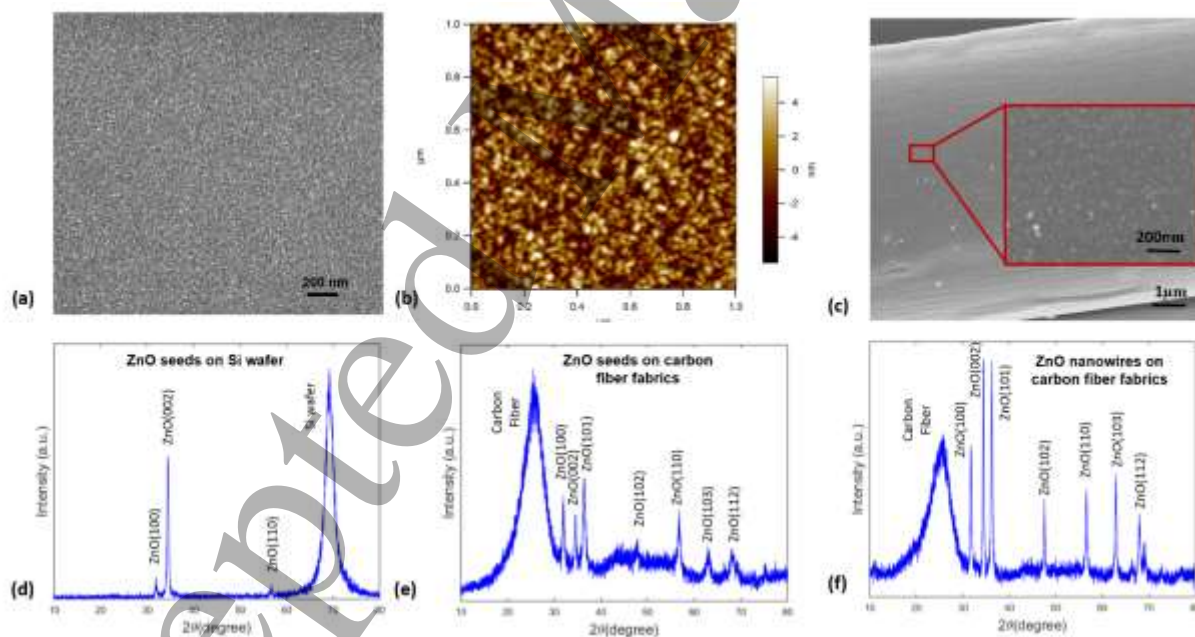


Fig. 1. (a) FESEM image of ZnO seeds on a silicon substrate; (b) AFM image of ZnO seeds on a silicon substrate; (c) FESEM image of ZnO seeds on carbon fiber fabrics; (d) XRD pattern of ZnO nucleation on the silicon substrate; (e) XRD pattern of ZnO nucleation on carbon fiber fabrics; (f) XRD pattern of ZnO nanowires on carbon fiber fabrics.


The morphology of ZnO nanoarrays on carbon fiber fabrics was studied using FESEM, as shown in Fig. 2. Six sets of ZnO nanoarrays were synthesized, varying the hydrothermal reaction temperature and reagents' concentrations. The hydrothermal synthesis time used was 17 hours for all the experiments. It

1
2
3 should be noted that the $\text{Zn}(\text{NO}_3)_2$ and HMT concentrations had a significant effect on ZnO morphology.
4 As shown in Fig. 2 a and b, ZnO nanowires were obtained when 25 mMol/L of $\text{Zn}(\text{NO}_3)_2$ and HMT were
5 used during the hydrothermal treatment. ZnO nanowires with similar morphology were obtained when the
6 hydrothermal reaction temperature was reduced to 70 °C. However, the average diameter of ZnO nanoarrays
7 significantly increased when 50 mMol/L of $\text{Zn}(\text{NO}_3)_2$ and HMT were used during the hydrothermal
8 treatment. As shown in Fig. 2 d and e, ZnO nanorods were synthesized on carbon fibers. Similar ZnO
9 nanorods were obtained when the hydrothermal reaction temperature was reduced to 70 °C, though both the
10 average diameter and length of ZnO nanorods were slightly reduced. The vertical alignment of ZnO
11 nanoarrays were visualized from the side view, as shown in Fig. 1 c and f. Good ZnO alignment of both
12 ZnO nanowires and nanorods were obtained from samples B1 and B2.
13
14

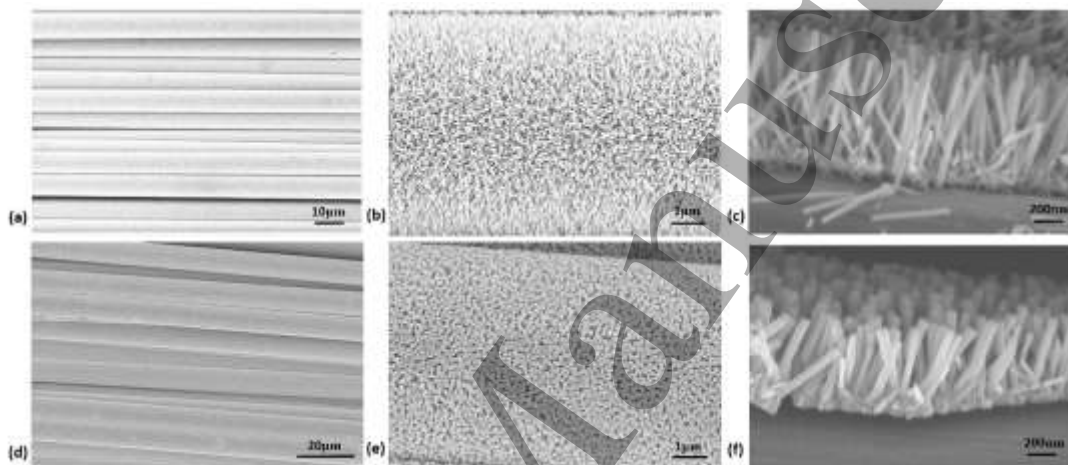

15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31 Fig. 2. (a - c) FESEM images of sample B1 showing the vertically aligned ZnO nanowires on carbon fibers;
32 (c - f) FESEM images of sample B2 showing the vertically aligned ZnO nanorods on carbon fibers.

33
34 When $\text{Zn}(\text{NO}_3)_2$ and HMT concentrations increased to 100 mMol/L, the diameter of ZnO nanorods
35 increased and the ZnO nanorods were grown at an increased density. As shown in Fig. 3, nanorods covered
36 entire carbon fiber. Similar results were obtained from sample B3 when the hydrothermal temperature
37 increased to 80 °C. Since this type of ZnO nanoarray coatings on carbon fibers did not significantly increase
38 the surface area to volume ratio of carbon fibers, we did not consider those samples for interfacial strength
39 enhancement in carbon fiber fabrics and composites.
40

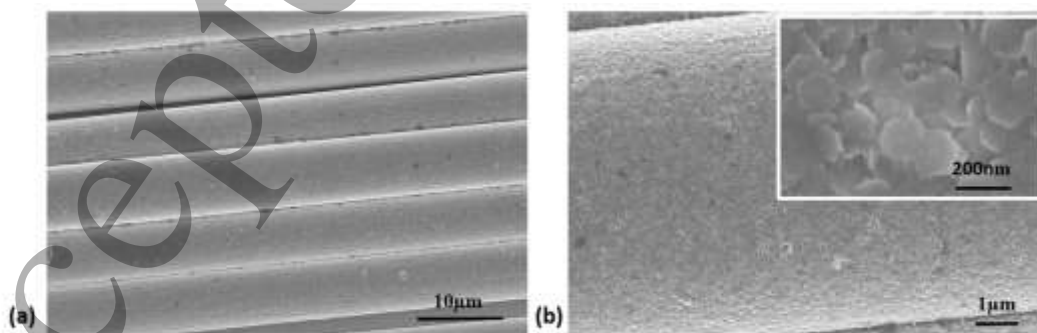

41
42
43
44
45
46
47
48
49
50
51
52 Fig. 3. FESEM images of sample A3 showing a top view of the fully grown ZnO nanorods covering the
53 entire carbon fiber.
54
55
56
57
58
59
60

The average diameters and the length to diameter ratio of ZnO are two critical parameters indicating potential mechanical property enhancement capabilities due to increased surface area on carbon fibers. As shown in Fig. 4, the averaged diameters of ZnO nanoarrays increased from 28 nm (sample A1) to 189 nm (sample B3), and the length to diameter ratio decreased from 270 (sample A1) to 44 (sample B3), when $\text{Zn}(\text{NO}_3)_2$ and HMT concentrations increased from 25 mMol/L to 100 mMol/L. The variation of ZnO diameter and length to diameter ratio proved that the solution concentration used in hydrothermal synthesis of ZnO nanoarrays on carbon fibers was the dominant effect on the ZnO morphology.

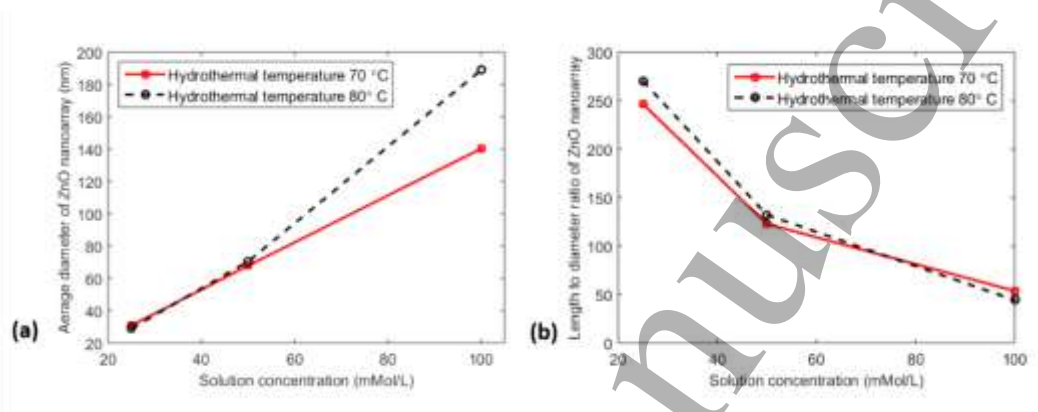


Fig. 4. (a) Average diameters of ZnO nanoarrays with different concentrations of hydrothermal solutions; (b) average length to diameter ratio of ZnO nanoarrays with different concentrations of hydrothermal solutions.

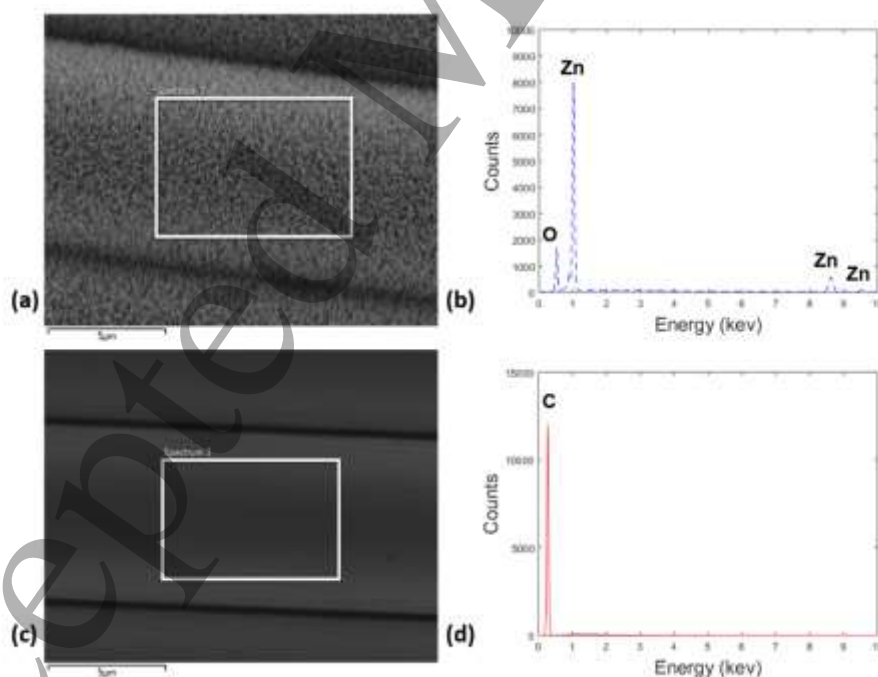


Fig. 5. (a) FESEM image on carbon fiber with ZnO nanowires; (b) EDX graph measured from the highlighted area in (a); (c) FESEM image on bare carbon fiber; (d) EDX graph measured from the highlighted area in (c).

The EDX pattern (Fig. 5 b) shows the elemental analysis on the ZnO nanoarrays coated carbon fiber fabrics. When carbon fibers with ZnO nanoarrays were tested using EDX, only zinc and oxygen elements were detected on the top surface, indicating the high density of ZnO nanoarrays. Although there were gaps among ZnO nanoarrays, the high length to diameter ratio of nanoarrays created full coverage of the carbon fiber surface. For comparison, when pristine carbon fibers were studied via EDX (Fig. 5 d), only carbon was detected.

The weight ratios of ZnO nanoarrays on carbon fibers were investigated using TGA tests and are shown in Fig 6. All the experiments were conducted by increasing the temperature by 5 °C/min. The weight of all samples began decreasing around 600 °C. ZnO modified carbon fibers reached full decomposition at 780 °C, and bare carbon fibers were fully decomposed at about 876 °C. Of the carbon fibers coated with ZnO nanoarrays, there was about 11 wt. % left after the TGA tests. Since only carbon was burned off during all the TGA tests, the residual weight was considered to be only ZnO, indicating about an 11 wt. % weight increase after ZnO nanoarrays synthesis on carbon fibers. In addition, the decomposition speed of bare carbon fibers was slower than the modified carbon fibers with ZnO nanowires. This is because the increased surface area to volume ratio on the modified carbon fibers increased heat transfer efficiency. Therefore, ZnO modified carbon fibers were burned off faster than their unmodified counterparts.

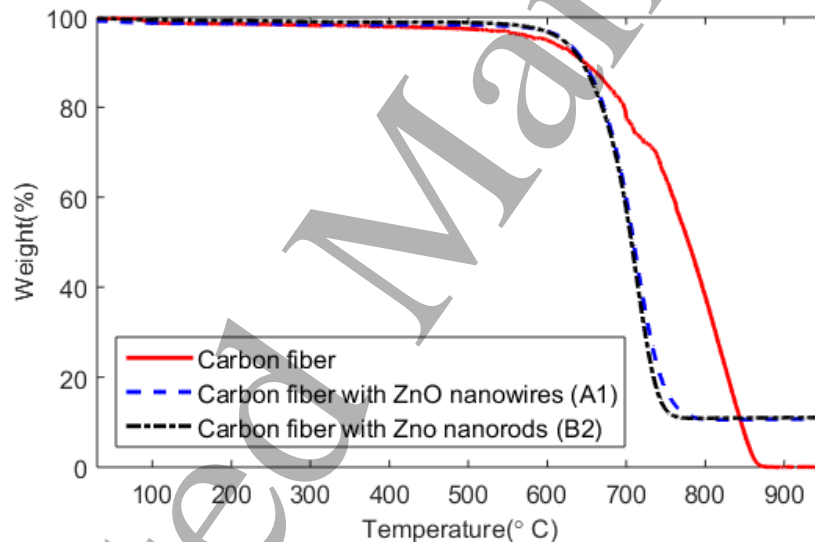


Fig. 6. TGA graphs of carbon fiber, and carbon fiber coated with ZnO nanoarrays.

4. Conclusions

This paper presents a two-step approach of vertically aligned ZnO nanoarrays synthesis on carbon fiber fabrics using the combined ALD and hydrothermal methods. The optimal ALD parameters and ZnO seeding procedure were identified using silicon substrates and adopted to grow the ZnO seeds on carbon fiber fabrics. The hydrothermal method was used to synthesize ZnO nanoarrays. By adjusting the hydrothermal solution concentration and temperature, the average diameters of ZnO nanowires and nanorods can be controlled between 28 nm and 189 nm, and the length to diameter ratio of nanowires and nanorods can be controlled between 270 and 44. All ZnO modified carbon fibers were characterized using FESEM, EDX, and TGA. Due to the dramatic increase of surface area on the modified carbon fiber fabrics, these materials can be used to develop novel structural composites with enhanced mechanical properties. Load sensing capabilities can also be obtained due to the piezoelectric properties of the ZnO nanoarray.

Acknowledgments

The authors appreciate the financial support from the National Science Foundation (award number: 1712178) and the SEED Funding for Interdisciplinary Research program in the Gallogly College of Engineering at the University of Oklahoma.

References

1. A. Mouritz, E. Gellert, P. Burchill, and K. Challis, *Review of advanced composite structures for naval ships and submarines*. Composite structures, 2001. **53**(1): p. 21-42.
2. T.X.H. Le, M. Bechelany, and M. Cretin, *Carbon felt based-electrodes for energy and environmental applications: A review*. Carbon, 2017. **122**: p. 564-591.
3. Z. Liu, J. Wang, V. Kushvaha, S. Poyraz, H. Tippur, S. Park, M. Kim, Y. Liu, J. Bar, and H. Chen, *Poptube approach for ultrafast carbon nanotube growth*. Chemical Communications, 2011. **47**(35): p. 9912-9914.
4. T.J. Athauda, P. Hari, and R.R. Ozer, *Tuning physical and optical properties of ZnO nanowire arrays grown on cotton fibers*. ACS applied materials & interfaces, 2013. **5**(13): p. 6237-6246.
5. T.J. Athauda, W.S. LePage, J.M. Chalker, and R.R. Ozer, *High density growth of ZnO nanorods on cotton fabric enables access to a flame resistant composite*. Rsc Advances, 2014. **4**(28): p. 14582-14585.
6. S. Soumya, S.N. Kumar, A.P. Mohamed, and S. Ananthakumar, *Silanated nano ZnO hybrid embedded PMMA polymer coatings on cotton fabrics for near-IR reflective, antifungal cool-textiles*. New Journal of Chemistry, 2016. **40**(8): p. 7210-7221.
7. M. Arfaoui, P. Dolez, M. Dubé, and É. David, *Development and characterization of a hydrophobic treatment for jute fibres based on zinc oxide nanoparticles and a fatty acid*. Applied Surface Science, 2017. **397**: p. 19-29.
8. F. Kayaci, S. Vempati, C. Ozgit-Akgun, N. Biyikli, and T. Uyar, *Enhanced photocatalytic activity of homoassembled ZnO nanostructures on electrospun polymeric nanofibers: A combination of atomic layer deposition and hydrothermal growth*. Applied Catalysis B: Environmental, 2014. **156**: p. 173-183.
9. M. Ashraf, P. Champagne, A. Perwuelz, C. Campagne, and A. Leriche, *Photocatalytic solution discoloration and self-cleaning by polyester fabric functionalized with ZnO nanorods*. Journal of Industrial Textiles, 2015. **44**(6): p. 884-898.
10. U. Galan, Y. Lin, G.J. Ehlert, and H.A. Sodano, *Effect of ZnO nanowire morphology on the interfacial strength of nanowire coated carbon fibers*. Composites Science and Technology, 2011. **71**(7): p. 946-954.
11. G.J. Ehlert, U. Galan, and H.A. Sodano, *Role of surface chemistry in adhesion between ZnO nanowires and carbon fibers in hybrid composites*. ACS applied materials & interfaces, 2013. **5**(3): p. 635-645.
12. A. Alipour Skandani, N. Masghouni, S.W. Case, D. Leo, and M. Al-Haik, *Enhanced vibration damping of carbon fibers-ZnO nanorods hybrid composites*. Applied Physics Letters, 2012. **101**(7): p. 073111.
13. L. Zhang, S. Bai, C. Su, Y. Zheng, Y. Qin, C. Xu, and Z.L. Wang, *A High-Reliability Kevlar Fiber-ZnO Nanowires Hybrid Nanogenerator and its Application on Self-Powered UV Detection*. Advanced Functional Materials, 2015. **25**(36): p. 5794-5798.
14. H.-S. Hwang, M.H. Malakooti, B.A. Patterson, and H.A. Sodano, *Increased inter yarn friction through ZnO nanowire arrays grown on aramid fabric*. Composites Science and Technology, 2015. **107**: p. 75-81.
15. H.-S. Hwang, M.H. Malakooti, and H.A. Sodano, *Tailored inter yarn friction in aramid fabrics through morphology control of surface grown ZnO nanowires*. Composites Part A: Applied Science and Manufacturing, 2015. **76**: p. 326-333.

16. Y. Liu, S. Mohanty, and A. Chattopadhyay, *Condition based structural health monitoring and prognosis of composite structures under uniaxial and biaxial loading*. Journal of Nondestructive Evaluation, 2010. **29**(3): p. 181-188.
17. Y. Liu and S. Nayak, *Structural health monitoring: State of the art and perspectives*. JOM, 2012. **64**(7): p. 789-792.
18. E.T. Thostenson and T.-W. Chou, *Real-time in situ sensing of damage evolution in advanced fiber composites using carbon nanotube networks*. Nanotechnology, 2008. **19**(21): p. 215713.
19. I. Kang, M.J. Schulz, J.H. Kim, V. Shanov, and D. Shi, *A carbon nanotube strain sensor for structural health monitoring*. Smart materials and structures, 2006. **15**(3): p. 737.
20. J. Elias, I. Utke, S. Yoon, M. Bechelany, A. Weidenkaff, J. Michler, and L. Philippe, *Electrochemical growth of ZnO nanowires on atomic layer deposition coated polystyrene sphere templates*. Electrochimica Acta, 2013. **110**: p. 387-392.
21. J. Conley Jr, L. Stecker, and Y. Ono, *Directed assembly of ZnO nanowires on a Si substrate without a metal catalyst using a patterned ZnO seed layer*. Nanotechnology, 2005. **16**(2): p. 292.
22. S.-Y. Pung, K.-L. Choy, X. Hou, and C. Shan, *Preferential growth of ZnO thin films by the atomic layer deposition technique*. Nanotechnology, 2008. **19**(43): p. 435609.
23. B. Weng, J. Wang, P. Larson, and Y. Liu, *Growth process optimization of ZnO thin film using atomic layer deposition*. Materials Research Express, 2016. **3**(12): p. 126402.